



# MTC510

## Epoxy Component Prepreg

### Introduction

MTC510 is an epoxy resin system designed to cure between 80°C and 120°C allowing flexibility in component manufacture. It is a toughened epoxy resin system designed for component manufacturing that can be supplied on a variety of fabrics and in UD format to meet your cost and manufacturing requirements.

**Typical applications:** *General purpose – Visual*

### Key Features & Benefits

- Cure temperature from **80°C to 120°C**
- Service temperature up to **120°C**
- Low CTE and shrinkage
- Work life at 20°C: **30 days**
- Storage life at -18°C: **12 months**
- Very low VOC content – no added solvents during manufacture
- Excellent surface finish

### Storage & Out Life

This material should be kept frozen at -18°C. It must be kept sealed in a polythene bag which must not be opened until fully thawed to room temperature. If the material is not fully used, then the material must be resealed in the polythene bag to prevent moisture absorption.

Unit 4  
The Reservation  
Sleaford Enterprise Park  
Sleaford  
Lincolnshire  
NG34 7BY

www.shdcomposites.com  
Tel: +44 (0) 1529 307629  
sales@shdcomposites.com



## Cure Cycles & performances

### CURE CYCLE OPTIONS:

Cure	Initial Min Cure	Tg
80°C (minimum)	16 hours	90°C
90°C	8 hours	100°C
100°C	4 hours	110°C
120°C (maximum)	1 hour	130°C

- Curing Schedule is meant to be a guide only and is subject to local conditions.
- To avoid exotherm particular care must be taken with thick laminates.  
Ramp rates must not exceed **3.0°C** per minute during **initial cure**.  
Ramp rates must not exceed **0.3°C** per minute during **post cure** (free standing).

- Typical Tg:

<b>DMA – Dry Tg</b>	120°C for 1hr	Tg E' Onset	<b>131 °C</b>	<i>Modified ASTM D7028 (Single Cantilever)</i>
		Tg Peak Tan $\delta$	<b>148 °C</b>	

Tests performed on **MTC510-C415T-HS-12K-38%RW** laminates



## Cured Material Properties

Tests performed on **MTC510-C200T-HS-3K-42%RW** laminates

(200gsm 2x2 twill, T300 3k carbon fabric)


Test	Results	Standard		
<b>Vf</b>	Fibre volume fraction	<b>49.41</b>	<b>%</b>	<i>BS EN ISO 14127 Method B</i>
<b>CPT</b>	Cured ply thickness	<b>0.237</b>	<b>mm</b>	<i>BS EN ISO 14127 Method B</i>
<b>Tensile 0°</b>	Tensile strength	<b>634</b>	<b>MPa</b>	<i>BS EN ISO 527-4</i>
	Tensile modulus	<b>55.7</b>	<b>GPa</b>	
	Poisson's ratio	<b>0.05</b>		
<b>Tensile 90°</b>	Tensile strength	<b>680</b>	<b>MPa</b>	
	Tensile modulus	<b>56.7</b>	<b>GPa</b>	
	Poisson's ratio	<b>0.05</b>		
<b>Compressive 0°</b>	Compressive strength	<b>683</b>	<b>MPa</b>	<i>prEN 2850 Type B</i>
	Compressive modulus	<b>51.0</b>	<b>GPa</b>	
<b>Compressive 90°</b>	Compressive strength	<b>691</b>	<b>MPa</b>	
	Compressive modulus	<b>52.6</b>	<b>GPa</b>	
<b>Flexural 0°</b>	Flexural strength	<b>946</b>	<b>MPa</b>	<i>BS EN ISO 14125</i>
	Flexural modulus	<b>56.7</b>	<b>GPa</b>	
<b>Flexural 90°</b>	Flexural strength	<b>885</b>	<b>MPa</b>	
	Flexural modulus	<b>53.2</b>	<b>GPa</b>	
<b>In-Plane Shear ±45°</b>	In-Plane shear strength (5% strain)	<b>65.3</b>	<b>MPa</b>	<i>BS EN ISO 14129</i>
	In-Plane shear strength (ultimate)	<b>115.0</b>	<b>MPa</b>	
	In-Plane shear modulus	<b>3.42</b>	<b>GPa</b>	
<b>Interlaminar Shear 0°</b>	Interlaminar shear strength	<b>71.1</b>	<b>MPa</b>	<i>BS EN ISO 14130</i>
<b>Interlaminar Shear 90°</b>	Interlaminar shear strength	<b>70.9</b>	<b>MPa</b>	
<b>DMA – Dry Tg</b> Initial cure	Tg E' Onset	<b>127</b>	<b>°C</b>	<i>Modified ASTM D7028 (Single Cantilever)</i>
	Tg Peak Tan δ	<b>137</b>	<b>°C</b>	
<b>DMA – Wet Tg</b> 14 days in water at 70°C	Tg E' Onset	<b>90</b>	<b>°C</b>	
	Tg Peak Tan δ	<b>100</b>	<b>°C</b>	

Mechanical testing carried out at 21±2°C. Initial cure: 15mins at 85°C followed by 1hr at 120°C, autoclave 6bar. All figures in this report are actual test results and have not been normalised. Testing was either completed by SHD Composites laboratories, or independently by UKAS approved organisations. Complete test reports can be supplied independently upon request.



## Viscosity Profile

Testing carried out using a rotational rheometer.

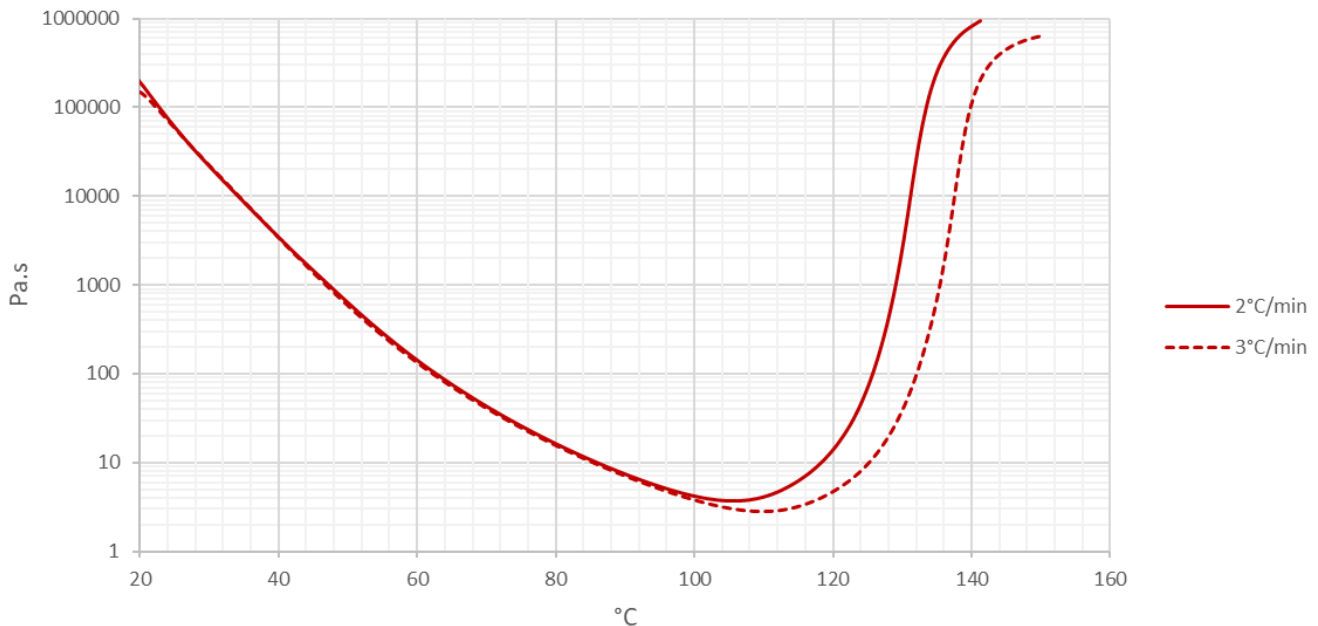

## Health and Safety

This material contains epoxy resin which can cause allergic reactions with skin contact and must avoid repeated and prolonged skin contact.

Please refer to the product Safety Data Sheet before using this material. The following precautions must be taken when using epoxy resin preregs:

- Overalls must be worn.
- Impervious gloves must be worn.
- Curing schedule is meant to be as a guide only and is subject to local conditions.
- To avoid exotherm, particular care must be taken with thick laminates.
- Ramp rates must not exceed 3.0°C/min during initial cure and 0.3°C/min during post cure.

**Disclaimer:** Technical advice, instruction, data or recommendation, whether verbal or in writing, is given in good faith. The SHD company providing any such advice gives no warranty or guarantee, whether express or implied, in relation to such advice.

Customers must carry out their own tests and assessments as necessary in order to determine the quality and suitability of the product for their particular application and circumstances. Such testing should be performed under conditions identical to those to which the final component/product may be subjected. Values listed in any SHD document are for typical properties of the product or substance in question and are not intended to be used in establishing either statistical specifications nor engineering basis values. They do not constitute either minimum or maximum values for the product or substance in question.